

Coarse Grained Microscopic Model of Glass Formers

Juan P. Garrahan¹ and David Chandler²

¹*Theoretical Physics, University of Oxford, 1 Keble Road, Oxford, OX1 3NP, U.K.*

²*Department of Chemistry, University of California, Berkeley, California 94720*

We introduce a coarse grained model for atomic glass formers. Its elements are physically motivated local microscopic dynamical rules parameterized by observables. Results of the model are established and used to interpret the measured behaviors of supercooled fluids approaching glass transitions. The model predicts the presence of a crossover from hierarchical super-Arrhenius dynamics at short length scales to diffusive Arrhenius dynamics at large length scales. This prediction distinguishes our model from other theories of glass formers, and can to be tested by experiment.

Introduction. This article introduces a microscopic model of glass forming supercooled liquids. It is a coarse grained model with local dynamical rules, the elements of which can be measured. The rules contain only the physical features of detailed balance, dynamic facilitation, and persistence of particle flow direction. Our analysis of the model indicates that these features are all that is required to explain the time dependent and thermal behaviors of supercooled glass forming liquids. For such systems, relaxation times grow rapidly with decreasing temperature T , usually more rapidly than exponentially in T^{-1} . This non-Arrhenius (or super-Arrhenius) temperature dependence often coincides with a relatively large change in heat capacity at the glass transition. On the other hand, liquids whose relaxation times grow in an Arrhenius fashion with decreasing temperature often display small changes in heat capacity at the glass transition. Apparent correlations like these between thermodynamic properties and relaxation times have led to a commonly held opinion that a finite temperature thermodynamic transition somehow underlies a glass transition (for a review of this and other views, see [1]). In contrast, our model explains the empirically observed correlations of relaxation and calorimetric properties at the glass transition without recourse to unusual or precipitous thermodynamics.

Our model is described in terms of a grid or lattice in space-time. Underlying this discrete picture are certain ideas about continuous atomic motions in a supercooled liquid. The first idea is that particle mobility is sparse. Most atomic motions are small amplitude vibrations and not diffusion steps. Most molecules are effectively jammed. The second idea is that particle mobility in a glass former is the result of facilitation [2, 3]. Specifically, a region of jammed atoms can become unjammed and thus exhibit mobility only when it is adjacent to a region that is already unjammed. This idea implies that mobile or unjammed particles form chains in space-time. Chains of mobile particles have been revealed by atomistic computer simulations of supercooled liquids [4]. The third idea is that mobility carries a direction, and it is possible for this direction to persist in a glass former for significant periods of time. This convective-like quality of particle motion is also revealed by the atomistic computer simulations of supercooled liquids [4].

To help illustrate how these ideas motivate a lattice model, Fig. 1(a) depicts a mostly jammed fluid of spheres (drawn in two dimensions for artistic convenience). It shows, schematically, how mobility is found in unjammed regions, and that directed motion in one of those regions might make similarly directed motion possible in adjacent regions. The arrows are drawn pointing parallel to the mean direction of facilitation, and anti-parallel to the mean direction of particle motion. Given that particles singly occupy finite volumes, the possible influence of facilitation falls in a cone, as indicated by the dashed lines in Fig. 1(a).

The point of each cone in Fig. 1(a) depicts a position that is made accessible to an atom by prior motion in the vicinity of that point. As large voids dissipate quickly in a dense material, the most likely motions are collective and complicated shuffling of several particles. This shuffling could have a number of causes. One possibility is the presence of local density that is slightly less than a constraining value. Whatever its precise nature, the collective motion will have a definite direction for a period of time. In highly networked systems, directional persistence will quickly dissipate, decreasing its effect on subsequent motion.

To capture these physical features, we use the coarse grained description depicted in Fig. 1(b). Space is divided into square or cubic regions with side lengths comparable to, but not smaller than, the bulk correlation length of the fluid. As such, equilibrium fluctuations in one cell are uncorrelated with those in another at the same point in time. Further, time is divided into discrete intervals or time steps of length δt long enough to discriminate whether mobility (i.e., significant particle displacement) has or has not occurred in a particular cell during that interval. An empty cell in Fig. 1(b) indicates a region that exhibits no mobility during that time step. A cell containing an arrow indicates a region that does exhibit mobility during that time step, and the direction of the arrow is anti-parallel to the direction of motion and therefore indicates the direction of facilitation.

This coarse grained catalog or description of dynamical behavior can be constructed from the trajectories of any system. In this sense, there is no approximation involved in its use. Were the system an ordinary liquid, a typical equilibrium configuration of the coarse grained

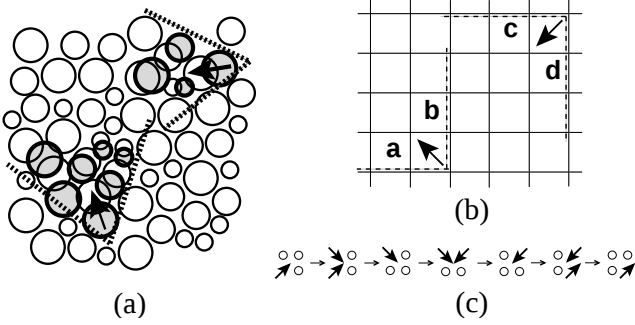


FIG. 1: (a) Facilitation of motion in a nearly arrested fluid. The arrows indicate direction of facilitation, anti parallel to direction of flow. Motion is facilitated in cones indicated by dotted lines. The white circles depict positions of atoms at one point in time; each grey circle, near a white circle of the same size, indicates the position of that near atom at a later point in time. (b) Coarse grained lattice description. The excitation at the bottom facilitates cells **a** and **b**, the excitation at the top, cells **c** and **d**. (c) Possible series of steps leading to a diffusive step in $d = 2$.

model would have essentially all regions occupied. For a sufficiently supercooled liquid, however, the concentration of arrows will be low. In that case, the thermodynamics of the material should be consistent with that of non-interacting arrows on a lattice. As a simplification, we shall consider only discrete orientations of the arrows, restricting them to lie along any one of the principal diagonals of its cell. Placing arrows along cell diagonals rather than edges allows for a cone of influence with positive angle. In particular, an arrow at a specific cell and time step can facilitate the creation or destruction of an arrow in a nearest neighbor cell at the next time step, where the vector drawn from the specific cell towards that nearest neighbor has a positive inner product with the arrow. For example, in Fig. 1(b), the arrow at the lower left can facilitate the birth of an arrow at the next time step in either cell labeled **a** or **b**. In this case, the cone of influence spans a quadrant in the square lattice, or an octant in the cubic lattice. Different cones of influence can be defined with different choices of spatial grids.

The model. As the preceding discussion indicates, our model describes the dynamics of the vector field $\mathbf{n}(\vec{x}) = n(\vec{x})\mathbf{v}(\vec{x})$, where $n(\vec{x}) = 1$ or 0 , depending on whether atoms in cell $\vec{x}$ are mobile or immobile, respectively, and $\mathbf{v}(\vec{x})$ is the unit vector pointing in the direction of the arrow in cell $\vec{x}$. For a square ($d = 2$) lattice, $\mathbf{v}(\vec{x})$ will be one of the four vectors $(\pm 1, \pm 1)/\sqrt{2}$. The equilibrium concentration of mobile cells is denoted by $c = \langle n(\vec{x}) \rangle$ (taking the lattice spacing to be unit length). The pointed brackets indicate equilibrium ensemble average. The system is isotropic, so that $\langle \mathbf{v}(\vec{x}) \rangle = 0$, and only trivial equal-time correlations exist so that $\langle \mathbf{n}(\vec{x})\mathbf{n}(\vec{y}) \rangle = 0$ for $\vec{x} \neq \vec{y}$. Accordingly, the equilibrium distribution for the vector field

is $P(\{\mathbf{n}(\vec{x})\}) = \prod_{\vec{x}} \rho[\mathbf{n}(\vec{x})]$, where

$$\rho(\mathbf{n}) \equiv g^{-n} (1 - c)^{1-n} c^n. \quad (1)$$

Here, g is the number of equally likely equilibrium orientations of an arrow [i.e., a vector $\mathbf{v}(\vec{x})$]. For the square (cubic) lattice, $g = 4$ ($g = 8$).

The passage from one time interval, t , to the next, $t + \delta t$, is governed in our model by the following single site Monte Carlo dynamics. Consider the transition at site $\vec{x}$ of the vector field $\mathbf{n}(\vec{x}) = n(\vec{x})\mathbf{v}(\vec{x})$ from an unexcited state, $n(\vec{x}) = 0$, to an excited state $n(\vec{x}) = 1$, $\mathbf{v}(\vec{x}) = \mathbf{w}$, and the corresponding backward transition. The dynamic facilitation described above is implemented by defining the corresponding rates as:

$$\mathbf{n}(\vec{x}) = 0 \xrightleftharpoons[\mathcal{C}_{\vec{x}}[\mathbf{w}] (1-c)]{\mathcal{C}_{\vec{x}}[\mathbf{w}] c/g} \mathbf{n}(\vec{x}) = \mathbf{w}, \quad (2)$$

where the kinetic constraint is implemented by the indicated state dependent rates, with $\mathcal{C}_{\vec{x}}[\mathbf{w}]$ given by

$$\mathcal{C}_{\vec{x}}[\mathbf{w}] = f \left[1 - \prod_{\langle \vec{y}, \vec{x} \rangle} \left(1 - \delta_{\sqrt{d}(\vec{x} - \vec{y}) \cdot \mathbf{n}(\vec{y}), 1} \right) \right] + (1 - f) \left[1 - \prod_{i=1}^d \left(1 - \delta_{\mathbf{n}(\vec{x} - \sqrt{d}\mathbf{w}_i), \mathbf{w}} \right) \right]. \quad (3)$$

Here, $\mathbf{w}_i$ indicates the i -th Cartesian component of $\mathbf{w}$, nearest neighbors are denoted by $\langle \vec{y}, \vec{x} \rangle$. Since $\mathcal{C}_{\vec{x}}[\mathbf{w}]$ does not depend on the state of the cell making the transition, but only on the state of its neighbours, it disappears from the ratio between forward and backward rates, and the dynamics defined by (2) satisfies detailed balance with respect to the distribution (1). The parameter $f \in [0, 1]$ in Eq. (3) determines the probability $p(f)$ that a newly created arrow will lie parallel to its facilitating arrow, $p(f) = [1 + f(g - 1)]^{-1}$. One of the extremes, $f = 1$, corresponds to the case where an excitation pointing in any direction can be created or destroyed as long as its site is facilitated by a neighbour. In the other extreme, $f = 0$, only excitations pointing in the same direction as the facilitating neighbour can be created or destroyed.

The above dynamics satisfies time reversal symmetry and detailed balance. It is designed to be physically realistic for c small, the realm of dynamical arrest in a glass former. When c is not small, the dynamics of a realistic system will proceed through other mechanisms in addition to facilitation. In general, even for c small, space and time coarse graining of an atomistic model will lead to transition rules with non-Markovian elements. We assume these elements are unimportant.

The parameters c and f have clear physical meaning. Observations of trajectories can determine the probability, c , that a microscopic region exhibits mobility over a specified microscopic time period. They can further determine f from the directional persistence probability

over a similar time period. For systems where directionality in particle motion can persist over a microscopic time δt (e.g., a nearly jammed fluid of hard spheres), f will be very small. For systems where directionality in particle motion will dissipate over that time (e.g., a highly networked fluid), f will be close to 1. One may use atomistic computer simulations of supercooled fluids to make the observations that determine c and f . Alternatively, one may perform microscopy on colloidal glass formers. In these cases, observed time scales relative to those of an ordinary liquid are modest in length. For glass forming supercooled liquids exhibiting long relative times scales, experiments using single molecule spectroscopic probes could be used.

The parameters c and f have energetic and entropic contributions. Since excitations in different sites are statically uncorrelated, their average concentration c must have the usual Boltzmann temperature dependence. Therefore, to the extent that c is small and mainly energetic, $-\ln(c/g)$ is proportional to reciprocal temperature, $1/T$. Similarly, since f is a local probability independent of the state of the system, it is natural to write $f = ac^b$ where a pertains mainly to its entropic contribution, and b pertains mainly to its energetic contribution.

Properties of the model. It is useful to begin by considering the two extreme limits of the model, the $f = 1$ case and the $f = 0$ case.

- $f = 1$. Here, motion of an arrow can proceed diffusively as illustrated with the seven step sequence configurations shown in Fig. 1(c). This sequence, involving single activation on three occasions, produces a single diffusive step in either $d = 2$ or 3. As such, the relaxation time for a length scale l , $\tau_{f=1}(l)$, will obey $\tau_{f=1}(l) \sim \delta t D^{-1} l^{z_1}$, where the dynamical exponent, z_1 , will be a constant, while the diffusion constant, D , will be proportional to c for $d = 2$ and 3. (The quantity D is the diffusion constant for excitations, which is distinct from the diffusion constant for particle motion.) Since the distance between arrows at equilibrium is $c^{-1/d}$, the system approaches equilibrium with time scale $\tau_{f=1} \sim \delta t c^{-\Delta_1}$ where for $d = 2$ and 3, $\Delta_1 = 1 + z_1/d$. From numerical simulations of the model on a square ($d = 2$) and cubic ($d = 3$) lattices, we find that $\Delta_1 \approx 2$. Simulation results for the relaxation of the model from a disordered state on a square lattice are shown in the left panel of Fig. 2. As expected from the diffusive nature of its motion, the behavior of this model is like that of the FA (i.e., one-spin-facilitated Fredrickson-Andersen [3, 6]) model. The Arrhenius dependence of $\tau_{f=1}$ on c is often called “strong” [1].

- $f = 0$. Here, the motion is hierarchical [7, 8], like that of the East model [6, 9] or its generalization to higher dimension [10], and it is ergodic for $d \geq 2$. An arrow can relax only through pathways involving like pointing arrows. For $d = 2$ the system is composed of a mixture of arrows of four different directions, with each direction uncoupled from the others. The dynamical behavior of

each of the four independent components is like that of a North-or-East model [10] which in turn behaves like the East model. In this case, therefore, $\tau_{f=0}(l) \sim \delta t l^{z_0}$ where now the dynamical exponent is not constant but rather a function of c , namely $z_0 \sim \ln(g/c)/\ln 2$, where c/g is the concentration of like directed arrows. Hence, close to equilibrium, the overall time scale for relaxation is $\tau_{f=0} \sim \delta t c^{-\Delta_0}$, where $\Delta_0 = z_0/d$. This scaling is consistent with the simulation results for $d = 2$ graphed in the right panel of Fig. 2. The super-Arrhenius dependence on c is often called “fragile” [1].

- $0 < f < 1$. Here, we adopt an interpolation formula by adding rates in series: $\tau^{-1}(l) \approx (1 - f) \tau_{f=0}^{-1}(l) + f \tau_{f=1}^{-1}(l)$. As such, for small f ,

$$\tau(l) \approx \delta t l^{z_0} \left(1 + D f l^{(z_0 - z_1)}\right)^{-1}. \quad (4)$$

The corresponding equilibrium relaxation time is therefore

$$\tau \approx \delta t c^{-\Delta_0} \left(1 + f c^{-(\Delta_0 - \Delta_1)}\right)^{-1}. \quad (5)$$

These equations exhibit a crossover behavior. In particular, for a given c and f , there is a crossover length, l_* , such that for $l > l_*$, relaxation is diffusive and thus Arrhenius, and for $l < l_*$, relaxation is hierarchical and super-Arrhenius. Thus, at large enough length scales, the relaxation of all systems, no matter how fragile, will obey diffusive behavior. The existence of the crossover length, l_* , could be demonstrated experimentally from the single molecule spectroscopy of rotating nanoparticle probes of various lengths. The existence of a crossover length also implies that there is a crossover c_* (or T_* if one associates c with T as suggested earlier) such that for $c < c_*$ (or $T < T_*$), the equilibrium relaxation time of the model is Arrhenius, and for $c > c_*$ (or $T > T_*$), it is super-Arrhenius. Implicit in these remarks is an appreciation for the presence of dynamic heterogeneity [8, 11], in this case including flow direction, but for limitations of space, we cannot discuss it further here.

Crossover behavior was already demonstrated for what can be considered a mean field version of our model [12]. The presence of a crossover has also been argued for on experimental grounds [13]. Figure 3 illustrates the consequent temperature dependence for the possible crossover behaviors predicted from our model. Graphs on the left are drawn as Arrhenius plots. Graphs on the right show the same quantities but scaled in the fashion proposed by Angell [1]. Notice the possibility that relaxation times may fall above the Arrhenius line in the Angell plot. This specific behavior has not been anticipated. It arises in systems where f is both small and mainly entropic (i.e., independent of c).

Comparison with experiment. The fundamental control parameter is c , and while this quantity could be measured directly, most existing experimental data observes the effects of changing c by changing temperature

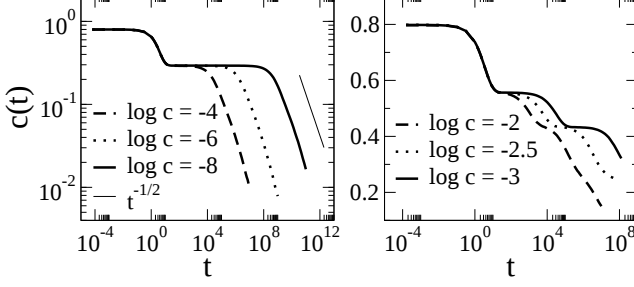


FIG. 2: Relaxation of the concentration $c(t)$ after a quench from an initial random state to final equilibrium concentration c in the $d = 2$ version of the model. Left panel: $f = 1$. Right panel: $f = 0$. Simulations were performed using continuous time Monte-Carlo [5], on system sizes $L = 10^5$ and averaged over 50 samples. Error bars are comparable to line thickness.

at the fixed pressure of 1 atm. To compare with that data, we therefore use

$$\ln\left(\frac{c}{1-c}\right) \approx \ln\left(\frac{c_R}{1-c_R}\right) - J\left(\frac{1}{T} - \frac{1}{T_R}\right), \quad (6)$$

where c_R is the concentration of mobile regions at a reference temperature T_R , and J is the enthalpy difference between a mobile and immobile region. Equation (6) is again based on the idea that since excitations at different spatial points (at equal times) are statically uncorrelated their average concentration c must have Boltzmann temperature dependence. Since mobile regions should be liquid like, and immobile regions should be solid like, we expect that J/T should be of the order of a few entropy units times the typical number of molecules in a cell (~ 10). With $\ln c$ linear in $1/T$, $\ln \tau_{f=0}$ is a quadratic polynomial in T^{-1} [14], while $\ln \tau_{f=1}$ is a linear one. A useful reference point, which allows for a direct comparison with previous analysis (eg., Ref. [15]), is $T_R = T_{1/2}$, the temperature at which the logarithm of the relaxation time is one half that at the glass transition. In this case $\tau_R \equiv \tau(c_R)$ is of the order of microseconds (μs). A common measure of fragility is $F_{1/2} \equiv 2T_g/T_{1/2} - 1$, where T_g is the glass transition temperature [15]. A second common measure is the steepness index, $m \equiv d \log \tau(T_g)/d(T_g/T)$ [16], i.e., the slope at T_g in the Angell plot. If the relaxation from $T_{1/2}$ to T_g follows the super-Arrhenius form of $\tau_{f=0}$, then $F_{1/2}$ and the elementary timescale δt determine m : $m_{f=0} = 32(1 - F_{1/2})^{-1}(1 + Y)(1 + 2Y)^{-1}$, where $Y = \log(\mu s/\delta t) [1 + \sqrt{1 + 4/\log(\mu s/\delta t)}]/8$. In the case of Arrhenius behaviour, or of an energetic crossover that takes place at $T > T_g$, the steepness index is given by $m_{f=1} = 16(1 - F_{1/2})^{-1}$, independent of δt .

Figure 4 shows that the ranges of fragility measures [15, 16] are well understood with our model. The dashed line corresponds to the value of $m_{f=0}$ in the case where

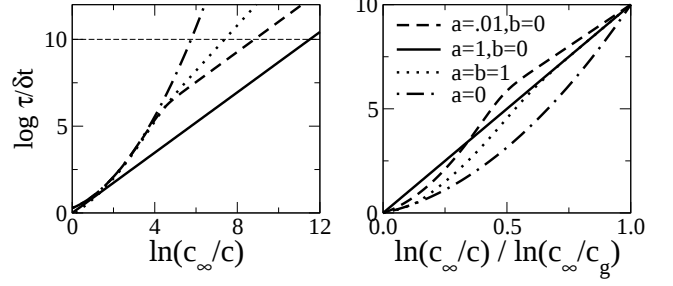


FIG. 3: Left panel: Arrhenius-like plot of relaxation time against equilibrium concentration, for various values of $f = a c^b$. The cases $a = 1, b = 0$ and $a = 0$ correspond to purely Arrhenius and super-Arrhenius behaviour, respectively. The case $a = b = 1$ leads to an energetic crossover, while $a = .01, b = 0$, to a mainly entropic one. Right panel: same as before now presented as an Angell-like plot, with the glass transition chosen at $\tau \sim 10^{10} \delta t$. $c_\infty = 8/9$ is the random concentration value for the cubic lattice.

$\delta t \sim \mu s$, $m_{f=0} = 32(1 - F_{1/2})^{-1}$. The full line is $m_{f=1}$. The region between this two lines, region I in Fig. 4, corresponds to super-Arrhenius behaviour $\tau_{f=0}$ with $\delta t \leq \mu s$. Most glass forming liquids fall in this region. Liquids on the full line are either those with purely Arrhenius behaviour or those that undergo an energetic crossover. Region II below the full line, corresponds to liquids which experience the entropic crossover noted above. Salol (SL) and α -phenyl-*o*-cresol (APOC) fall in this region. Region III above the dashed line corresponds to values of m which are too large to account with the present approach (except with $\delta t \gg \mu s$, which seems unphysical). Since selenium forms polymer chains, a feature not accounted for in our model, it is perhaps not surprising that it falls in this region [17].

In Fig. 5 we show Angell plots in the regime near T_g for five representative liquids from Fig. 4 (data from [18]). It shows fits to the dielectric relaxation timescale of 3-bromopentane (3BP) and viscosity of ortho-terphenyl (OTP), using $\tau_{f=0}$, and an Arrhenius fit to the viscosity data of GeO_2 , using $\tau_{f=1}$. It also illustrates the crossover in the the viscosity data of APOC and SL. The fits to the kinetic data determine the parameters of the model. From the coefficients of the terms quadratic in T_g/T in $\log \tau_{f=0}$, and from the linear one in $\log \tau_{f=1}$, we obtain the values of $J/T_g = (16.7, 26.7, 29.3, 31.8, 22.6)$ for (3BP, OTP, APOC, SL, GeO_2). These values of J/T_g obtained from fitting kinetic data agree with the expectations of our model.

Further, from the linear and constant terms in $\log \tau_{f=0}$, we determine $\log(\delta t/\mu s) = (-3.3, -4.4, -4.7, -4.8)$ and $\log(c_g/g) = (-3.2, -3.4, -3.6, -3.9)$, for (3BP, OTP, APOC, SL), respectively, so that in these cases δt is of the order of fractions of ns. These are physically reasonable times to discern whether or not a microscopic region exhibits mobility. We also obtain a re-

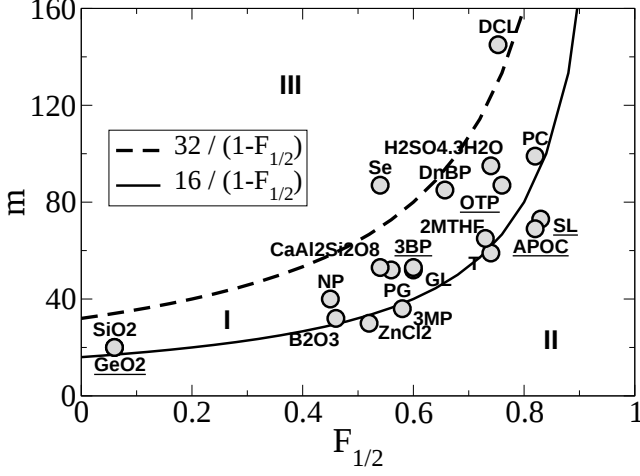


FIG. 4: Steepness index m against kinetic fragility $F_{1/2}$ for various supercooled liquids.

lation between the concentration at $T_{1/2}$, to that at the glass transition, $\log\{c_g(1 - c_{1/2})/[c_{1/2}(1 - c_g)]\} = (-1.5, -1.4, -1.5, -1.8, -4.6)$, for (3BP, OTP, APOC, SL, GeO₂). This list of ratios could in principle be checked experimentally. Fits to kinetic data do not determine the value of the parameter g . If we assume $g \approx 8$ as in the lattice model, then we obtain for the previous liquids: $\log c_g = (-2.3, -2.5, -2.7, -3.0, -3.6)$, where in the case of GeO₂ we have taken $c_{1/2} \sim O(1)$. Notice that the mobility concentration at T_g of the two purely super-Arrhenius liquids, 3BP and OTP, is at least an order of magnitude larger than that of the purely Arrhenius one, GeO₂. Moreover, the two liquids which display a crossover have intermediate values of c_g .

The order of magnitude difference between fragile and strong liquids (OTP and 3BP versus GeO₂ in our example) in concentration of mobility excitations at T_g is a crucial theoretical prediction of our approach. In the context of the model this difference has a clear origin. Relaxation time grows with decreasing c much faster in the fragile case ($f = 0$) than it in the strong case ($f = 1$). Thus, an arbitrarily specified long relaxation time (e.g., some minutes) coinciding to a glass transition is reached at a value of c in the fragile case that is much larger than that in the strong case.

The phenomenological consequences of this difference in concentrations are important. For example, $1/c^{1/d}(T)$ sets the dynamic correlation length, which in turn gives an upper bound for the size of dynamical heterogeneities [8]. Assuming that each cell contains about 5 to 10 molecules, so that $\delta x \approx 1\text{--}1.5$ nm, we estimate that the size of dynamic heterogeneities for 3BP, OTP and GeO₂ are bounded from above by 5–8 nm, 6–9 nm and 15–24 nm, respectively. As we have stressed [8], dynamic heterogeneity is self-similar over a range of lengths. Therefore, at a specific thermodynamic state point, no single

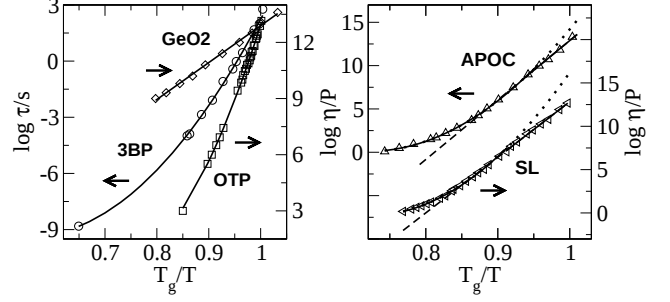


FIG. 5: Angell plots of dielectric relaxation and viscosity. In the left panel, solid lines for 3BP and OTP refer to $\tau_{f=0}$, and solid line for GeO₂ refers to $\tau_{f=1}$. In right panel full line corresponds to Eq. (5); dotted and dashed lines indicate $\tau_{f=0}$ and $\tau_{f=1}$ behaviour before and after the crossover. Symbols indicate experimental data.

length scale can be attributed to dynamic heterogeneity. Nevertheless, experimentalists have reported results for a few fragile liquids as if there is but a single specific length [11, 20]. The reported experimental lengths are consistent with our predicted bounds, though a definite comparison between theory and experiment must await more complete experimental information on the full range of heterogeneity lengths. Since $1/c_g$ is larger in the strong case than the fragile case, our model predicts that the size of dynamical heterogeneous regions in strong liquids should be appreciably larger than those in fragile liquids. This predicted trend is opposite of that made by other theoretical approaches, like frustrated limited domains [21] or random first order transitions [19].

From the concentrations c_g and the corresponding values of J/T_g we are able to predict the jumps in specific heats at T_g . According to our model, this heat capacity (per mol) relative to that of the solid is

$$\Delta c_p(T_g) \approx (J/T_g)^2 c_g \mathcal{N} + O(c_g^2), \quad (7)$$

where $\mathcal{N}$ is the number of molecules that contribute to enthalpy fluctuations per mobile cell. With the values obtained from the fits to the kinetic data for OTP, 3BP and GeO₂, for example, we obtain, $\Delta c_p(T_g)/\mathcal{N} \sim 2.3, 1.3, 0.13$, respectively. These values are in the ratio 17 : 10 : 1, which compares well to the experimental values $\Delta c_p(T_g)/k_B \sim 13.6, 9.2, 0.84$ [22], whose ratio is 16 : 11 : 1.

Further comparisons between this theory and experiment illustrating subtle counter examples to the usual correlation between super-Arrhenius behaviour and Δc_p [23] are left to future papers. Along with comparisons to equilibrium properties, illustrated herein, our model can be applied to out-of-equilibrium behaviors without further assumptions.

Acknowledgments. We are grateful to C.A. Angell for

discussions, and to H.C. Andersen, D. Reichman, F. Ritort, and F.H. Stillinger for discussions and constructive comments on an earlier version of this paper. This work was supported at Oxford by the Glasstone Fund and EP-

SRC Grant No. GR/R83712/01, and at Berkeley in its early stages by the NSF, and at its later stages by the US Department of Energy grant DE-FG03-87ER13793.

-
- [1] Angell, C.A. (1995) *Science* **267**, 1924; Debenedetti, P.G., & Stillinger, F.H. (2001) *Nature* **410**, 259.
 - [2] Glarum, S.H. (1960) *J. Chem. Phys.* **33**, 639; Phillips, M.C., Barlow A.J., & Lamb, J. (1972) *Proc. R. Soc. Lond. A* **329**, 193.
 - [3] Fredrickson, G.H., & Andersen, H.C. (1984) *Phys. Rev. Lett.* **53**, 1244.
 - [4] Perera, D.N., & Harrowell, P. (1998) *J. Non-Cryst. Solids* **235**, 314; Donati, C., Douglas, J.F., Kob, W., Plimpton, S.J., Poole, P.H., & Glotzer, S.C. (1998) *Phys. Rev. Lett.* **80**, 2338.
 - [5] Newman, M.E.J., & Barkema, G.T. (1999) *Monte Carlo Methods in Statistical Physics* (OUP, Oxford).
 - [6] For a general review of facilitated dynamics see Ritort, F., & Sollich, P. (2003) *Adv. in Phys.* **52**, 219.
 - [7] Palmer, R.G., Stein, D.L., Abrahams, E., & Anderson, P.W. (1984) *Phys. Rev. Lett.* **53**, 958.
 - [8] Garrahan, J.P., & Chandler, D. (2002) *Phys. Rev. Lett.* **89**, 035704.
 - [9] Jäckle, J., & Eisinger, S. (1991) *Z. Phys. B* **84**, 115; Sollich, P., & Evans, M.R. (1999) *Phys. Rev. Lett.* **83**, 3238.
 - [10] Our generalization of the East model (Ref. [6, 9]) to $d = 2$ is the North-or-East model, where a tagged spin is facilitated by a single nearest neighbor up spin that lies either above *or* to the right.
 - [11] For reviews on dynamic heterogeneity, see, Sillescu, H. (1999) *J. Non-Cryst. Solids* **243**, 81; Ediger, M.D. (2000) *Annu. Rev. Phys. Chem.* **51**, 99.
 - [12] Buhot, A., & Garrahan, J.P. (2001) *Phys. Rev. E* **64**, 021505.
 - [13] Ito, K., Moynihan, C.T., & Angell, C.A. (1999) *Nature (London)* **398**, 492.
 - [14] The T^{-2} form was considered by Bässler, H. (1987) *Phys. Rev. Lett.* **58**, 767.
 - [15] Martinez, L.M., & Angell, C.A. (2001) *Nature (London)* **410**, 663.
 - [16] Bohmer, R., Ngai, K.L., Angell, C.A., & Plazek, D.J. (1993) *J. Chem. Phys.* **99**, 4201.
 - [17] Bohmer, R., & Angell, C.A. (1993) *Phys. Rev. B* **48**, 5857.
 - [18] Berberian, J.G., & Cole, R.H. (1986) *J. Chem. Phys.* **84**, 6921; Napolitano, A., & Macedo, P.B. (1968) *J. Res. NBS* **72A**, 425; Laughlin, W.T., & Uhlmann, D.R. (1972) *J. Phys. Chem.* **76**, 2317.
 - [19] Xia, X., & Wolynes, P.G. (2000) *Proc. Natl. Acad. Sci. USA* **97**, 2990.
 - [20] Reinsberg, S.A., Heuer, A., Doliwa, B., Zimmermann H., & Spiess, H.W. (2002) *J. Non-Cryst. Solids* **307**, 208.
 - [21] Viot, P., Tarjus, G., & Kivelson, D. (2000) *J. Chem. Phys.* **112**, 10368.
 - [22] Chang, S.S., & Bestul, A.B. (1972) *J. Chem. Phys.* **56**, 503; Takahara, S., Yamamuro, O., Matsuo, T. (1995) *J. Phys. Chem.* **99**, 9589; Brüning, R., & Crowell, T. (1999) *J. Non-Cryst. Solids* **248**, 183.
 - [23] Huang, D., & McKenna, G.B. (2001) *J. Chem. Phys.* **114**, 5621.